



Product Information: CORNING® Eagle XG™ AMLCD GLASS SUBSTRATES

08/11

DESCRIPTION

Glass Type - Alkaline Earth Boro-Aluminosilicate
Forms Available - Fusion drawn Sheet
Principle Uses - Substrates for Active Matrix flat panel displays

PROPERTIES

Mechanical

	Metric	English
Density (20°C, 68°F)	2.38g/cc	148.5lb/ft ³
Young's Modulus	73.6 GPa	10.7 x 10 ⁶ psi
Shear Modulus	30.1 GPa	4.4 x 10 ⁶ psi
Poisson's Ratio		0.23
Vickers Hardness (200 gm load, 25 sec dwell)		640

Thermal Expansion

0 - 300°C	31.7 x 10 ⁻⁷ /°C (0 - 300°C)	17.7 x 10 ⁻⁷ /°F (32 - 572°C)
Room Temperature To Setting Point	35.5 x 10 ⁻⁷ /°C (25 - 675°C)	19.7 x 10 ⁻⁷ /°F (77 - 1247°C)

Thermal Conductivity

Thermal Conductivity is a calculated value, and is equal to the product of the Thermal diffusivity multiplied by Specific Heat multiplied by Density of the glass.


Temp (°C)	Specific Heat (J/gm-°K)	Thermal Diffusivity (cm ² /sec)	Thermal Conductivity (W/cm-°K)
23	0.768	0.00601	0.0109
100	0.896	0.00572	0.0122
200	0.998	0.00546	0.0129
300	1.067	0.00530	0.0134
400	1.110	0.00522	0.0137
500	1.154	0.00518	0.0142

Viscosity


Working Point (10 ⁴ poises)	1293°C
Softening Point (10 ^{7.6} poises)	971°C
Annealing Point Strain Point (10 ¹³ poises)	722°C
Strain Point (10 ^{14.5} poises)	669°C

Electrical

Log₁₀ Volume Resistivity (ohm-cm)
12.0 (250°C, 482°F)

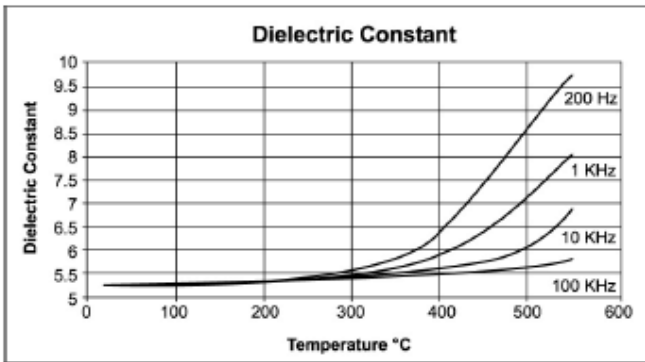

Dielectric Constant: 5.27
(20°C/68°F – 1 kHz)

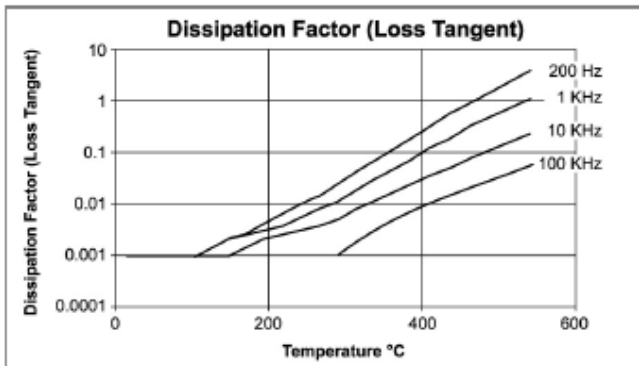

Loss Tangent: 0.30%
(20°C/68°F – 1 kHz)

Chemical

Weathering: 1

Weathering is defined as corrosion by atmospheric-borne gases and vapor such as water and carbon dioxide. Glasses rated 1 will almost never show weathering effects, those rated 2 will occasionally be troublesome, particularly if weathering products cannot be removed, those rated 3 require more careful consideration.

Durability:

Durability is measured via weight loss per surface area after immersion. Values are highly dependent upon actual testing conditions. Data is reported for Code 200F and Corning 1737F glasses run concurrently. Unless otherwise noted, concentrations refer to weight percent.

Reagent	Time	Temp	Weight Loss (mg/cm ²)
HCl – 5%	24 hrs	95°C	0.79
HNO ₃ – 1M	24 hrs	95°C	0.49
HF – 10%	20 min	20°C	5.18
NH ₄ F:HF – 10%	20 min	20°C	0.84
1HF:10HNO ₃	3 min	20°C	1.48
1HF:100HNO ₃	3 min	20°C	0.16
DI H ₂ O	24 hrs	95°C	0.00
Na ₂ CO ₃ – 0.02N	6 hrs	95°C	0.16
NaOH – 5%	6 hrs	95°C	1.83

Total alkali content is approximately: 0.1 wt%
(Typical < 0.05 wt%)

Optical Wavelength	Refractive Index
435.8 nm	1.5198
467.8 nm	1.5169
480 nm	1.5160
508.6 nm	1.5141
546.1 nm	1.5119
589.3 nm	1.5099
643.8 nm	1.5078

Birefringence Constant
331 (nm/cm)/(kg/mm²)